

Zinc Pinc- $\Delta 10$

Lab 3-Sili-Closeness



Ceramic
Materials
Workshop

ceramicmaterialsworkshop.com

Zinc Pinc


Original

030823-1

Neph Sy	40.00
Zinc Oxide	20.00
EPK	10.00
Flint	30.00
Chrome Oxide	1.00
Water	80



1-3 Second Dip

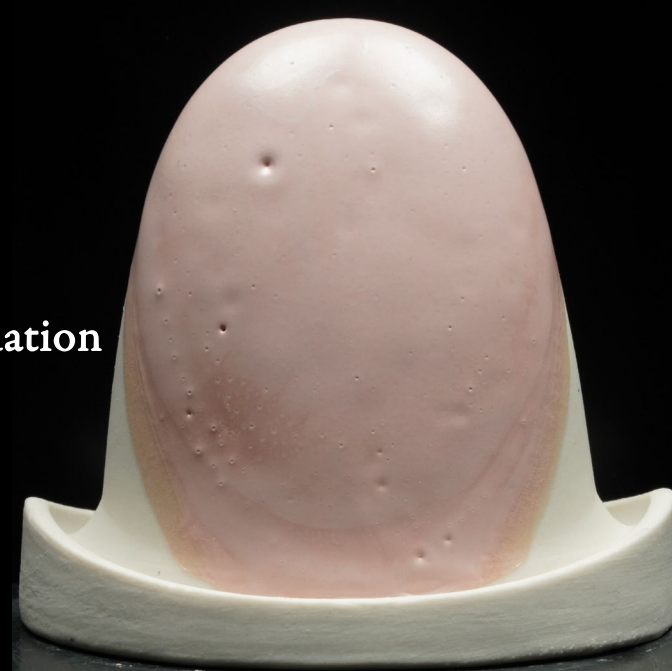

2-3 Second Dips




Reduction



Oxidation

UMF

SiO ₂ :Al ₂ O ₃ Ratio 8.00 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 2.93	Collective "Al ₂ O ₃ " 0.37	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.36	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

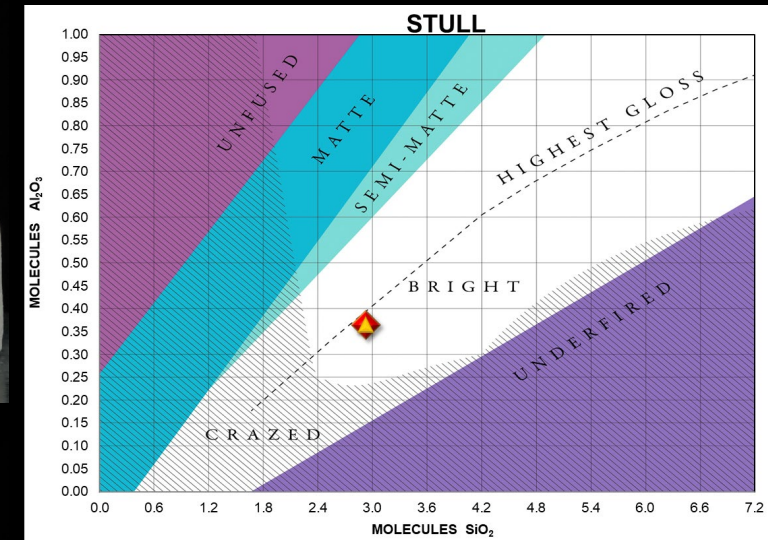


EUMF



SiO ₂ :Al ₂ O ₃ Ratio 8.00 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 2.93	Collective "Al ₂ O ₃ " 0.37	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.36	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

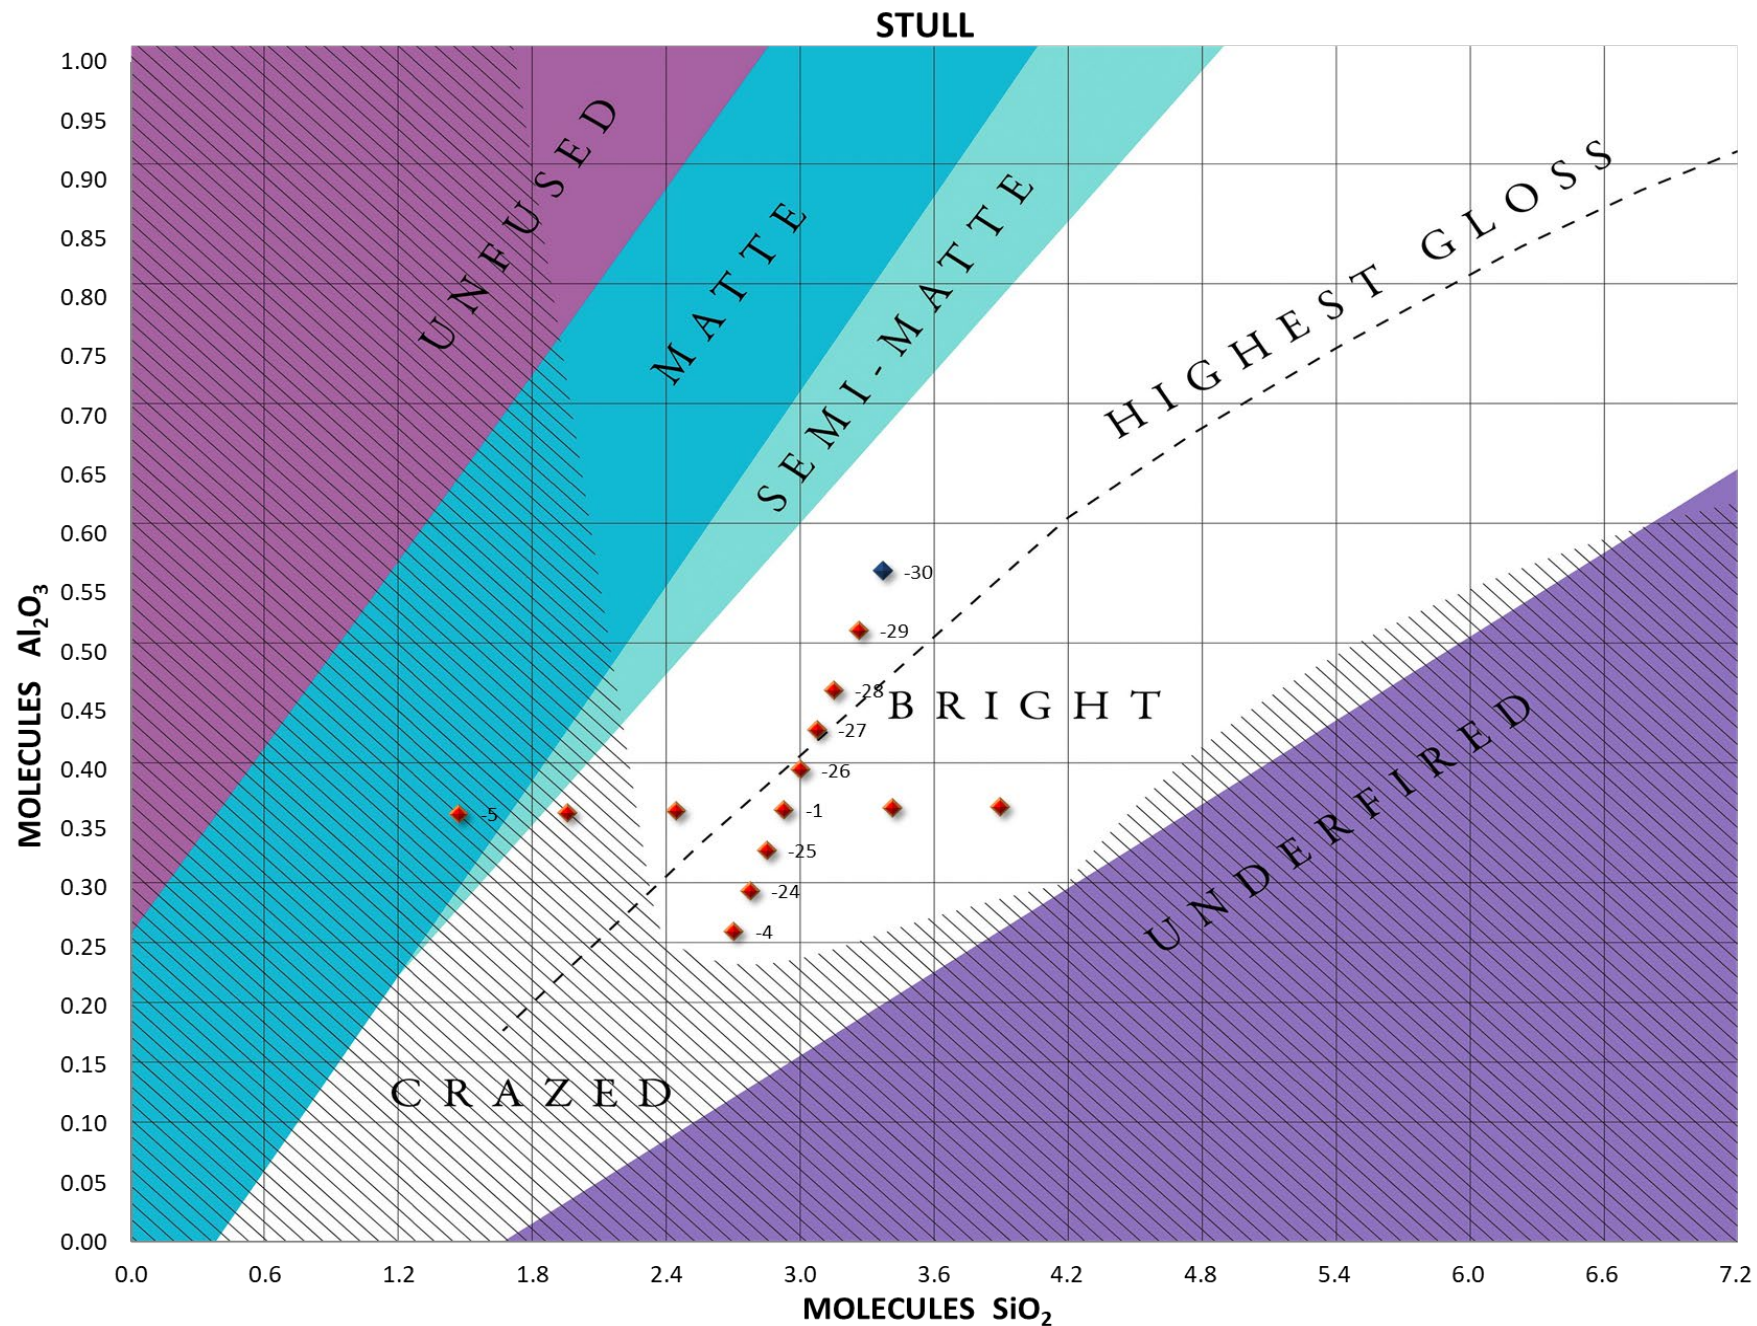


Full Test-Oxidation-1-3 Second Dip

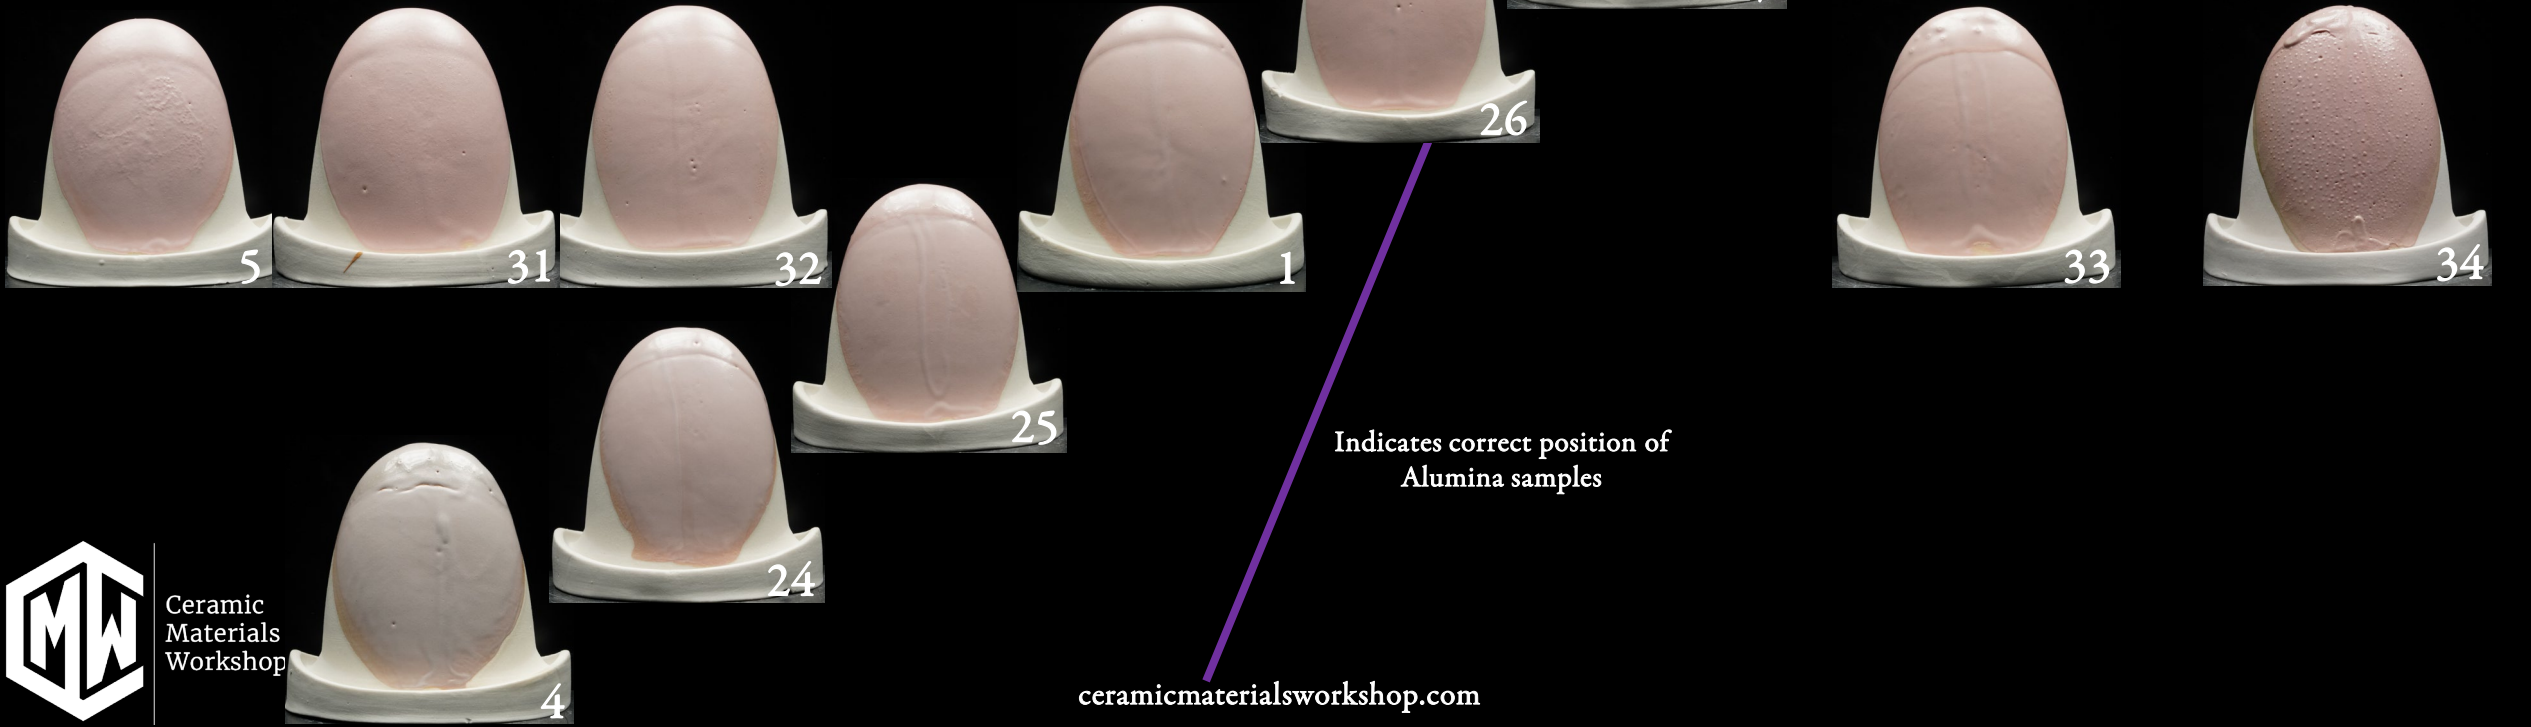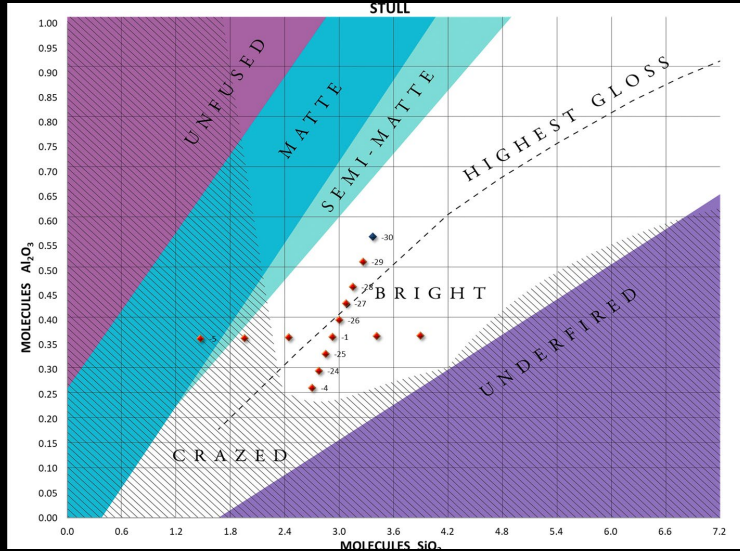

Indicates correct position of
Alumina samples

Full Test-Oxidation-2-3 Second Dips

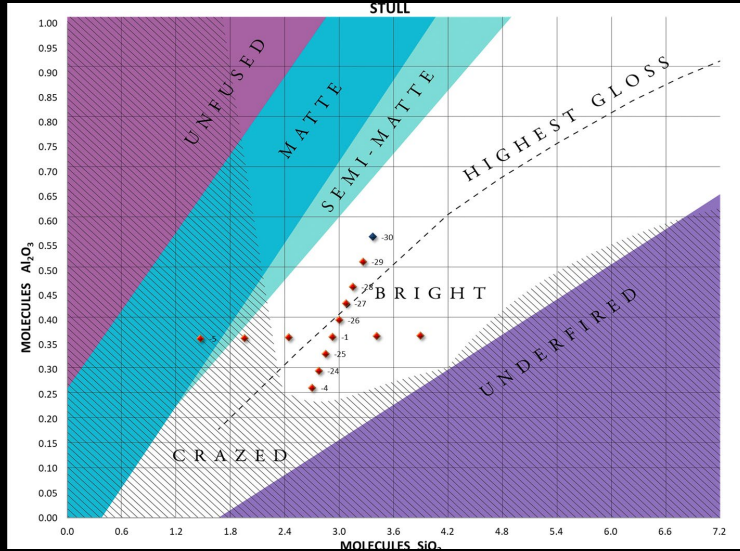

Silica Variations-Oxidation

1-3 Second Dip



030822-5



030822-31



030822-32



030822-1




030822-33




030822-34

2-3 Second Dips

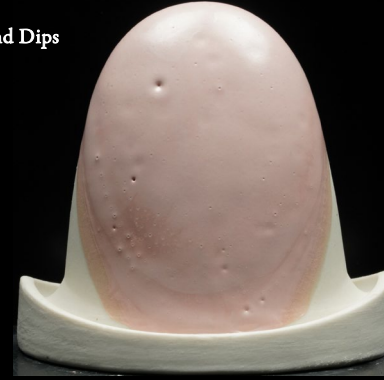


Ceramic
Materials
Workshop

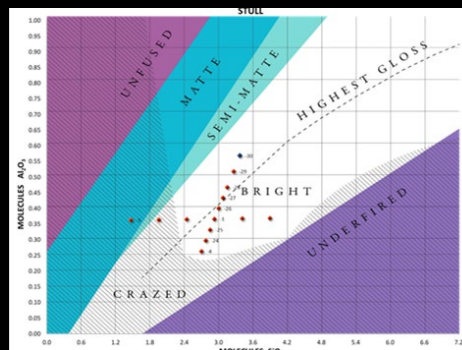

ceramicmaterialsworkshop.com


Alumina Variations-Oxidation

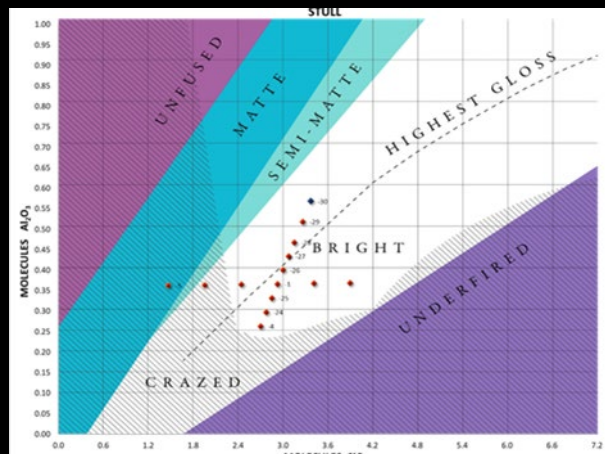


Ceramic
Materials
Workshop

ceramicmaterialsworkshop.com

Full Test-Reduction-1-3 Second Dip

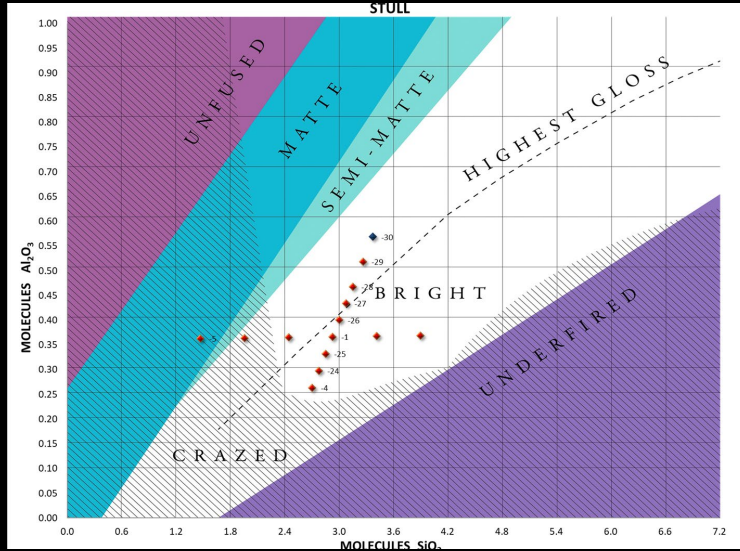

Full Test-Reduction-2-3 Second Dips

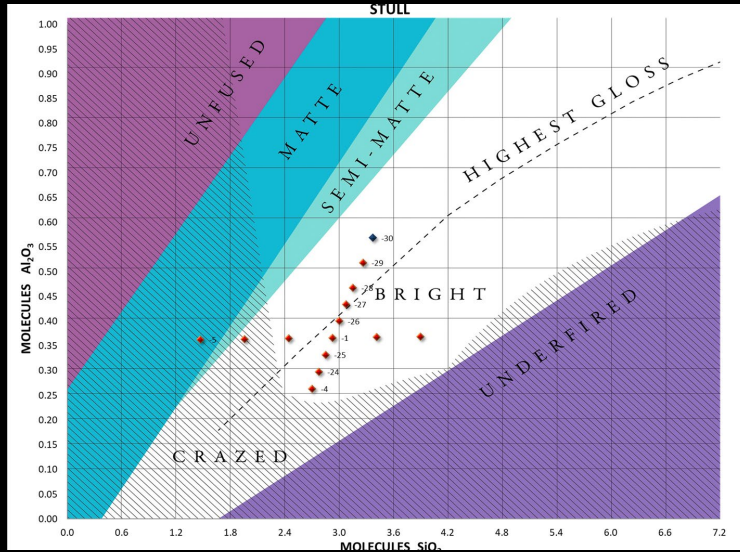

Silica Variations-Reduction

1-3 Second Dip



030822-5



030822-31



030822-32



030822-1




030822-33



030822-34

2-3 Second Dips

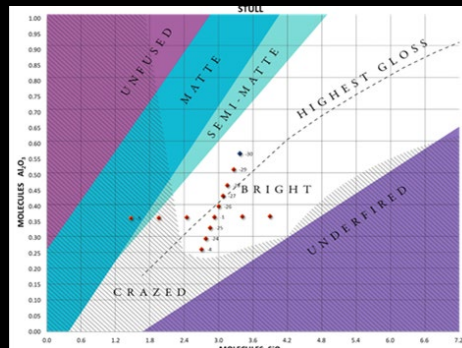


ceramicmaterialsworkshop.com




Ceramic
Materials
Workshop

Alumina Variations-Reduction

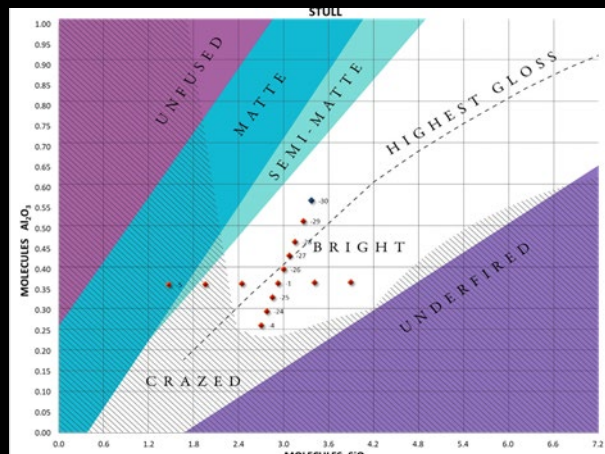

Ceramic
Materials
Workshop

ceramicmaterialsworkshop.com

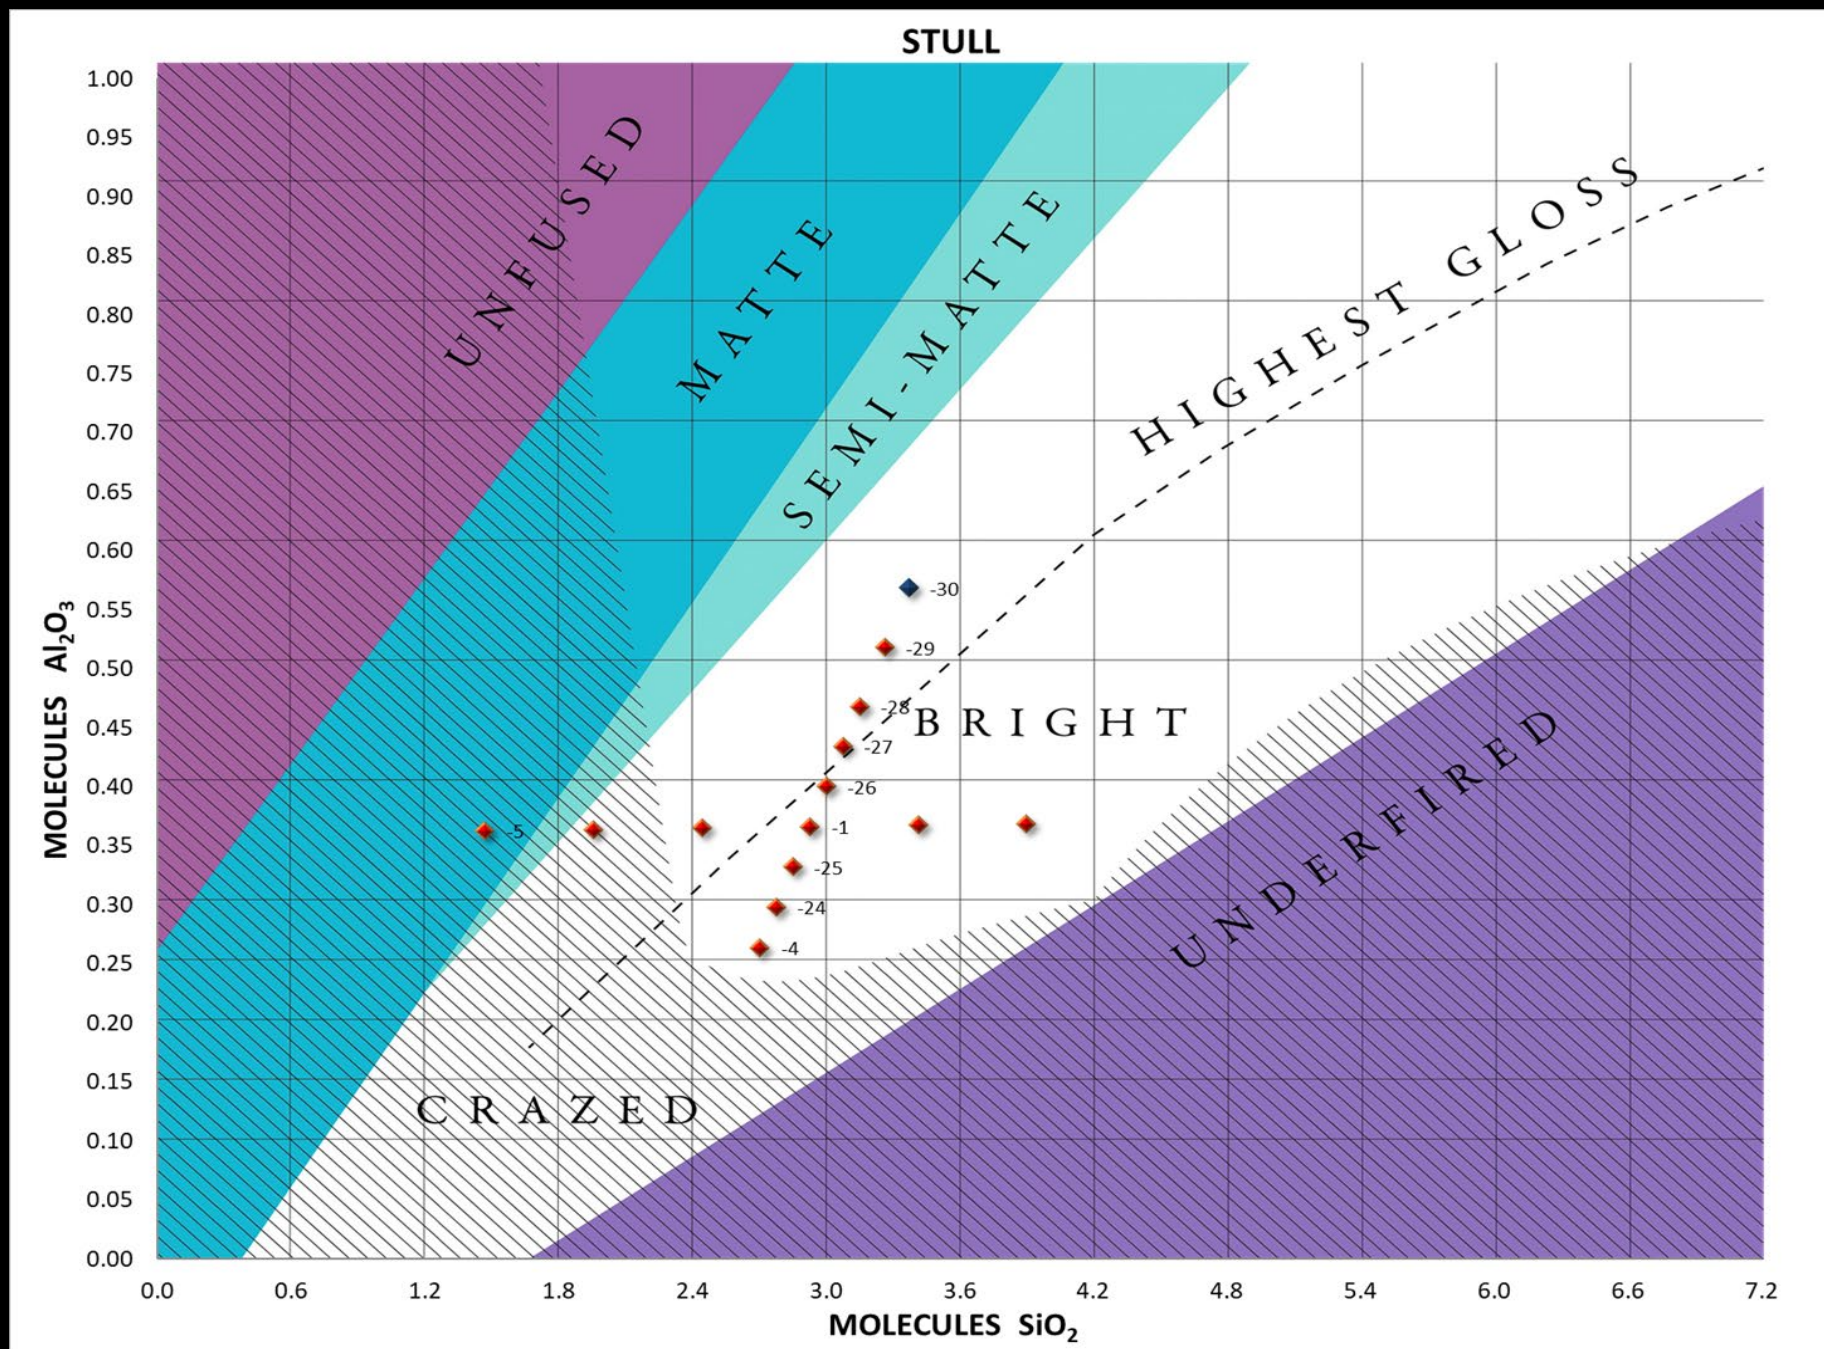

Zinc Pinc


Original

030823-1

Neph Sy	40.00
Zinc Oxide	20.00
EPK	10.00
Flint	30.00
Chrome Oxide	1.00
Water	80



1-3 Second Dip

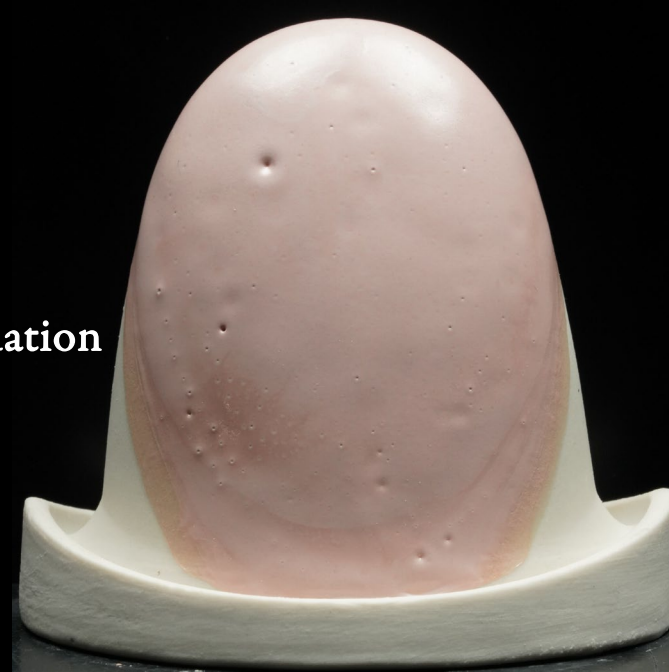

2-3 Second Dips

Oxidation




Reduction



UMF

SiO ₂ :Al ₂ O ₃ Ratio 8.00 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 2.93	Collective "Al ₂ O ₃ " 0.37	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.36	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

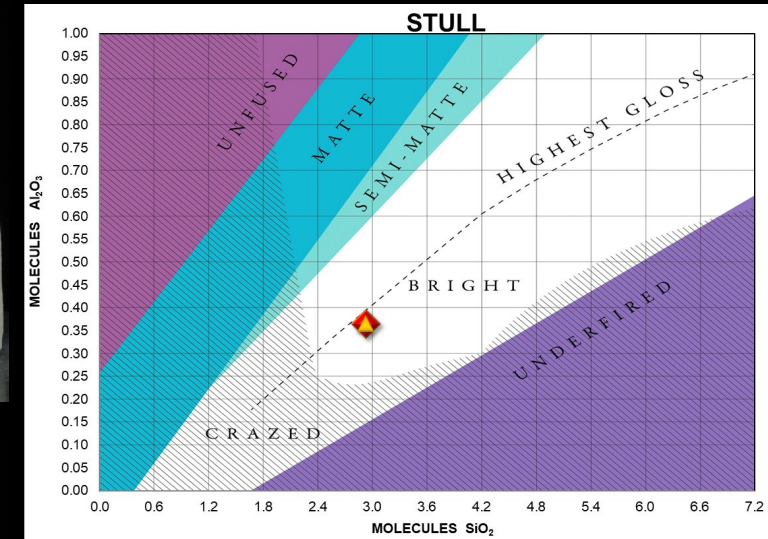

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 8.00 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 2.93	Collective "Al ₂ O ₃ " 0.37	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.36	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

ceramicmaterialsworkshop.com

Zinc Pinc

w/o Kaolin

030823-4

Neph Sy	44.44
Zinc Oxide	22.22
EPK	
Flint	33.33
Chrome Oxide	1.00
Water	80



1-3 Second Dip

Oxidation



2-3 Second Dips




Reduction



UMF

SiO ₂ :Al ₂ O ₃ Ratio 10.26 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 2.70	Collective "Al ₂ O ₃ " 0.26	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.26	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.00
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

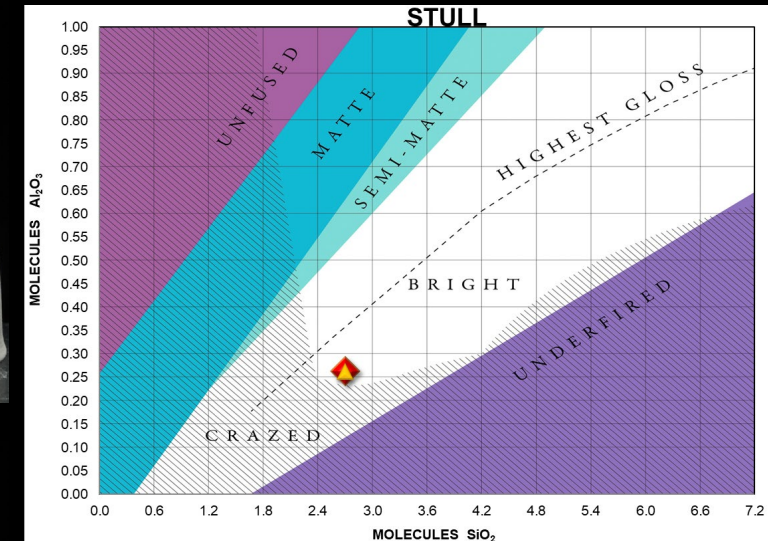

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 10.26 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 2.70	Collective "Al ₂ O ₃ " 0.26	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.26	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.00
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

ceramicmaterialsworkshop.com

Zinc Pinc

w/o Silica

030823-5

Neph Sy	57.14
Zinc Oxide	28.57
EPK	14.29
Flint	
Chrome Oxide	1.00
Water	80



1-3 Second Dip



2-3 Second Dips




Reduction



Oxidation

UMF

SiO ₂ :Al ₂ O ₃ Ratio 4.06 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 1.47	Collective "Al ₂ O ₃ " 0.36	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.36	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.00
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

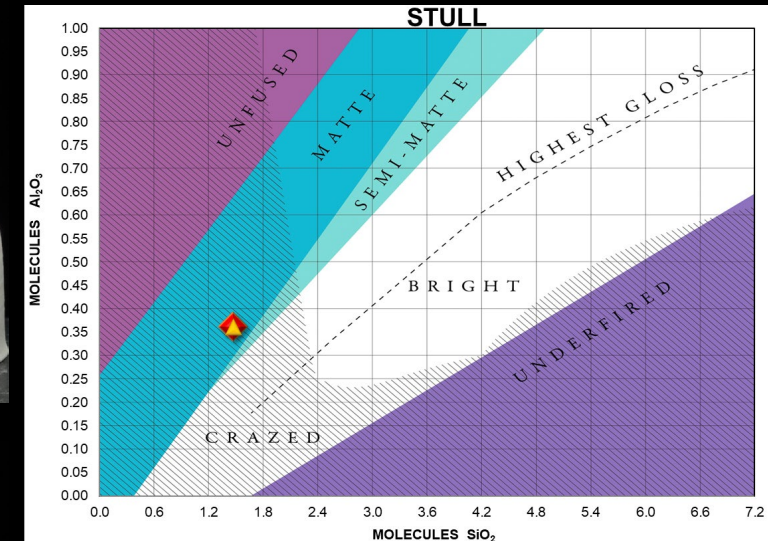

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 4.06 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 1.47	Collective "Al ₂ O ₃ " 0.36	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.36	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.00
Cr ₂ O ₃ 0.01	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

Zinc Pinc

Mapping
Kaolin 2

030823-24

Neph Sy	42.86
Zinc Oxide	21.43
EPK	3.57
Flint	32.15
Chrome Oxide	1.00
Water	80



1-3 Second Dip



2-3 Second Dips




Reduction



Oxidation

UMF

SiO ₂ :Al ₂ O ₃ Ratio 9.33 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 2.78	Collective "Al ₂ O ₃ " 0.30	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.30	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.00
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

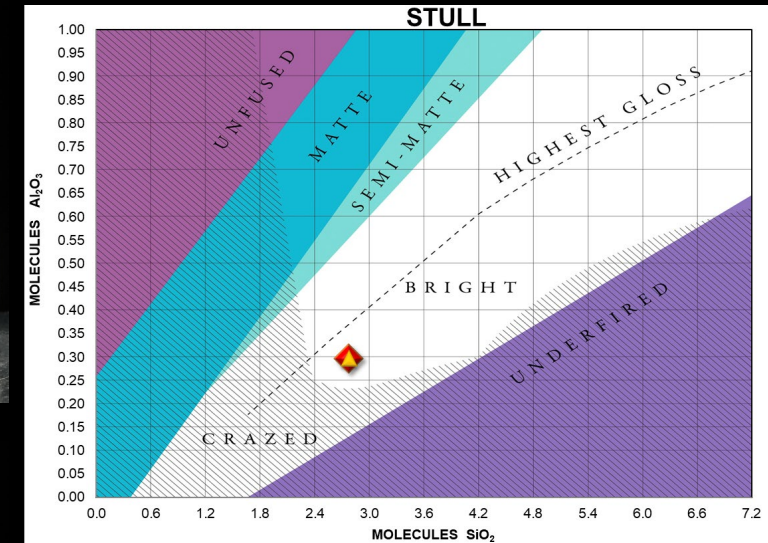

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 9.33 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 2.78	Collective "Al ₂ O ₃ " 0.30	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.30	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.00
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

ceramicmaterialsworkshop.com

Zinc Pinc

Mapping
Kaolin 3
030823-25

Neph Sy	41.38
Zinc Oxide	20.69
EPK	6.89
Flint	31.04
Chrome Oxide	1.00
Water	80



1-3 Second Dip



2-3 Second Dips




Reduction



UMF

SiO ₂ :Al ₂ O ₃ Ratio 8.59 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 2.85	Collective "Al ₂ O ₃ " 0.33	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.33	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

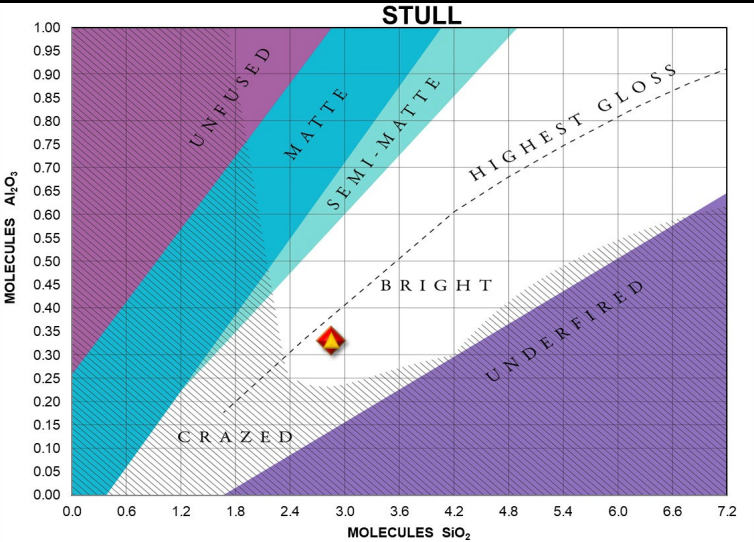

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 8.59 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 2.85	Collective "Al ₂ O ₃ " 0.33	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.33	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

Zinc Pinc

Mapping
Kaolin 5
030823-26

Neph Sy	38.71
Zinc Oxide	19.36
EPK	12.90
Flint	29.03
Chrome Oxide	1.00
Water	80



1-3 Second Dip



2-3 Second Dips




Reduction



Oxidation

UMF

SiO ₂ :Al ₂ O ₃ Ratio 7.51 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.00	Collective "Al ₂ O ₃ " 0.40	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.40	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

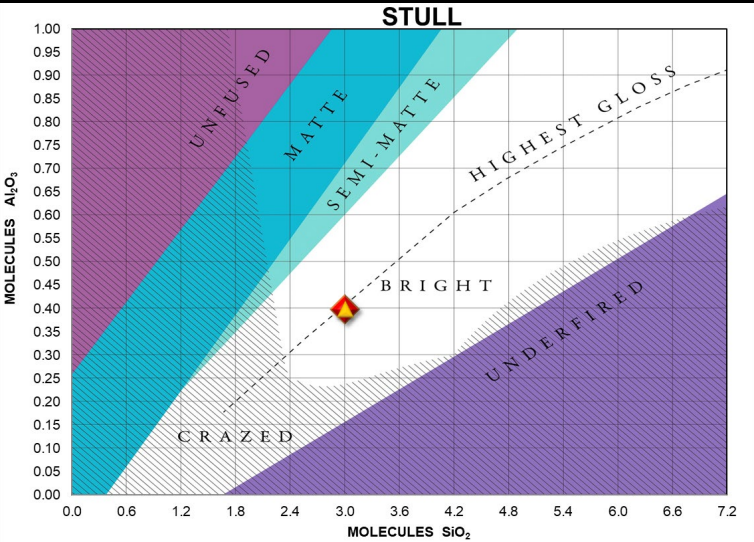

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 7.51 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.00	Collective "Al ₂ O ₃ " 0.40	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.40	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

Zinc Pinc

Mapping
Kaolin 6

030823-27

Neph Sy	37.50
Zinc Oxide	18.75
EPK	15.62
Flint	28.13
Chrome Oxide	1.00
Water	80



1-3 Second Dip



2-3 Second Dips




Reduction



Oxidation

UMF

SiO ₂ :Al ₂ O ₃ Ratio 7.09 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.08	Collective "Al ₂ O ₃ " 0.43	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.43	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

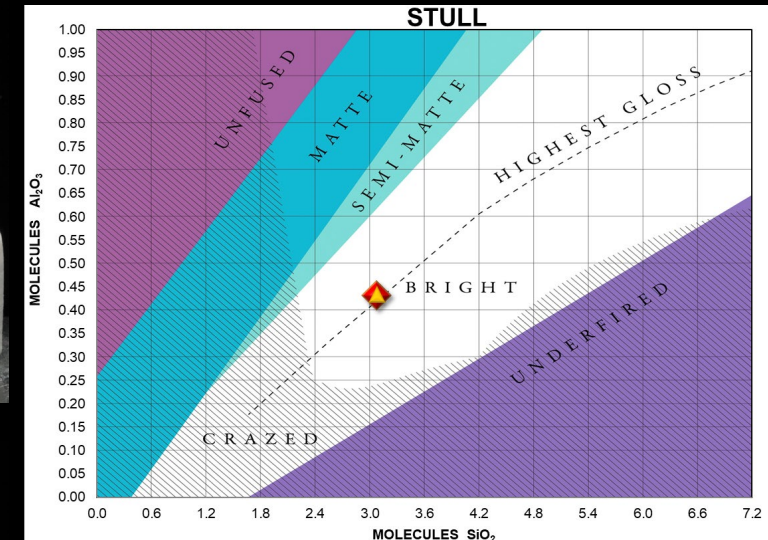

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 7.09 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.08	Collective "Al ₂ O ₃ " 0.43	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.43	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

ceramicmaterialsworkshop.com

Zinc Pinc

Mapping
Kaolin 7

030823-28

Neph Sy	36.36
Zinc Oxide	18.18
EPK	18.18
Flint	27.27
Chrome Oxide	1.00
Water	80



1-3 Second Dip



2-3 Second Dips




Reduction



Oxidation

UMF

SiO ₂ :Al ₂ O ₃ Ratio 6.74 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.15	Collective "Al ₂ O ₃ " 0.47	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.46	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.72	FeO 0.01
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

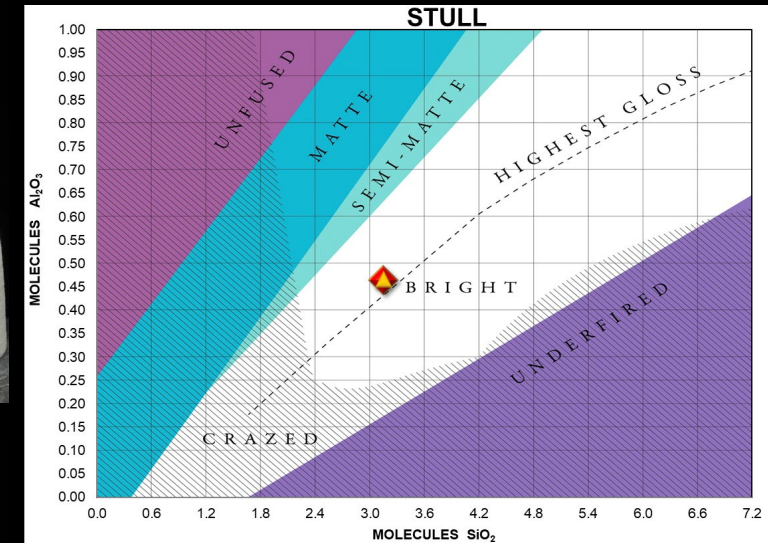

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 6.74 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.15	Collective "Al ₂ O ₃ " 0.47	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.46	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.72	FeO 0.01
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

Zinc Pinc

Mapping

Kaolin 8

030823-29

Neph Sy	34.78
Zinc Oxide	17.39
EPK	21.74
Flint	26.09
Chrome Oxide	1.00
Water	80



1-3 Second Dip



2-3 Second Dips




Reduction



Oxidation

UMF

SiO ₂ :Al ₂ O ₃ Ratio 6.30 :1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.26	Collective "Al ₂ O ₃ " 0.52	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.51	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.72	FeO 0.01
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

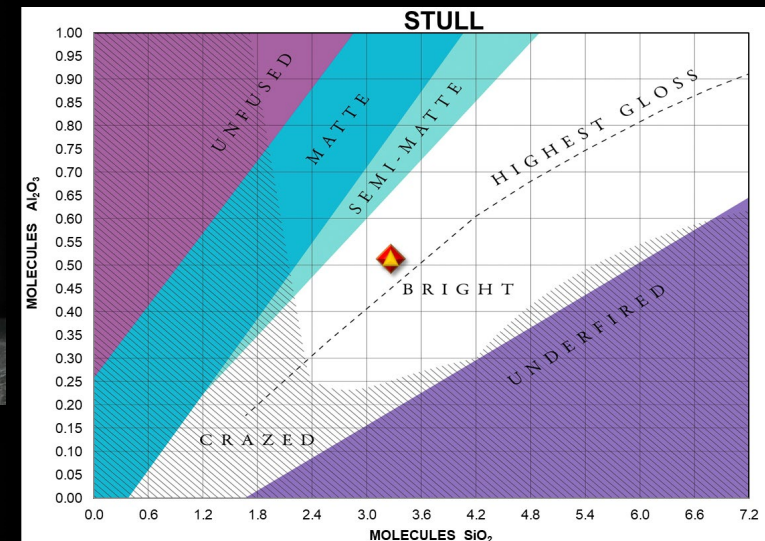

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 6.30 :1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.26	Collective "Al ₂ O ₃ " 0.52	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.51	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.72	FeO 0.01
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

Zinc Pinc

Mapping
Kaolin 9

030823-30

Neph Sy	33.33
Zinc Oxide	16.67
EPK	25.00
Flint	25.00
Chrome Oxide	1.00
Water	80



1-3 Second Dip



2-3 Second Dips




Reduction



Oxidation

UMF

SiO ₂ :Al ₂ O ₃ Ratio 5.94 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.37	Collective "Al ₂ O ₃ " 0.57	Na ₂ O 0.19	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.56	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.72	FeO 0.01
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

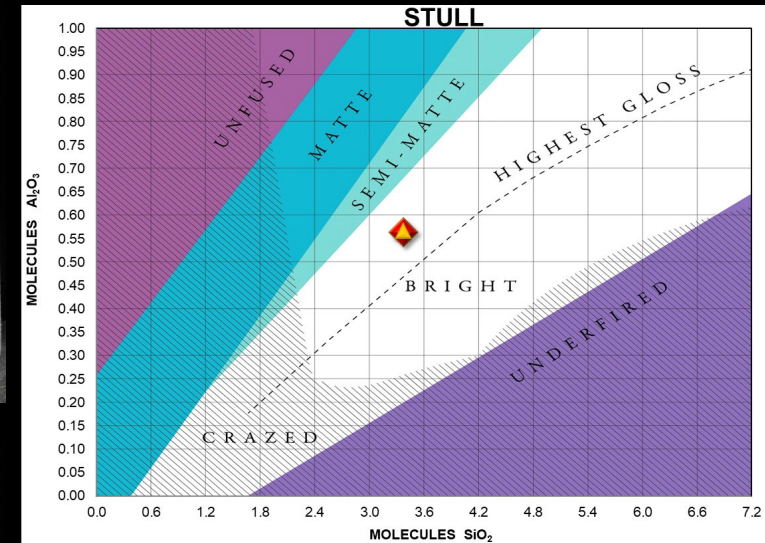

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 5.94 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.37	Collective "Al ₂ O ₃ " 0.57	Na ₂ O 0.19	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.56	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.72	FeO 0.01
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

Zinc Pinc

Mapping
Silica 2

030823-31

Neph Sy	50.00
Zinc Oxide	25.00
EPK	12.50
Flint	12.50
Chrome Oxide	1.00
Water	80



1-3 Second Dip



2-3 Second Dips




Reduction



Oxidation

UMF

SiO ₂ :Al ₂ O ₃ Ratio 5.38 :1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 1.96	Collective "Al ₂ O ₃ " 0.36	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.36	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

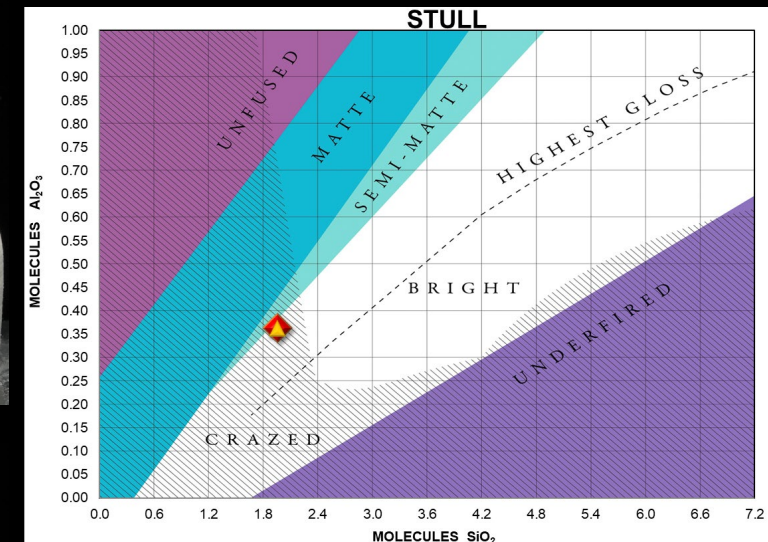

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 5.38 :1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 1.96	Collective "Al ₂ O ₃ " 0.36	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.36	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

Zinc Pinc

Mapping
Silica 3

030823-32

Neph Sy	44.44
Zinc Oxide	22.22
EPK	11.11
Flint	22.22
Chrome Oxide	1.00
Water	80



1-3 Second Dip



2-3 Second Dips




Reduction



Oxidation

UMF

SiO ₂ :Al ₂ O ₃ Ratio 6.69 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 2.44	Collective "Al ₂ O ₃ " 0.37	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.36	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

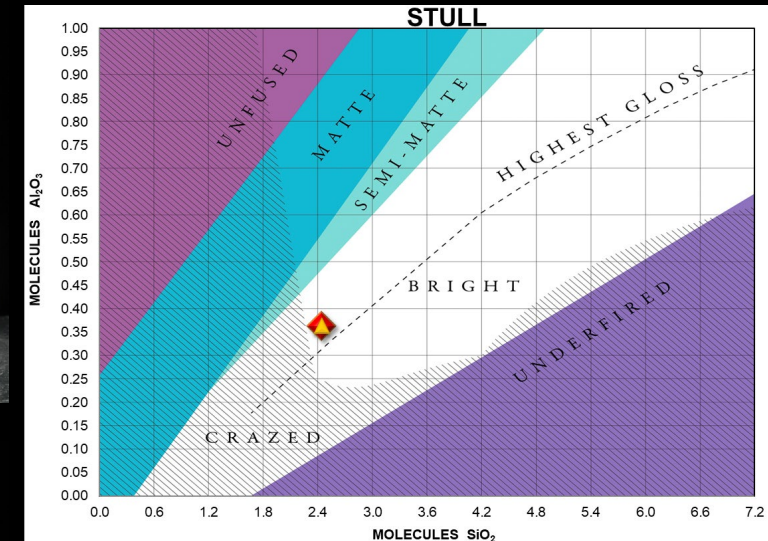

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 6.69 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 2.44	Collective "Al ₂ O ₃ " 0.37	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.36	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

Zinc Pinc

Mapping
Silica 5
030823-33

Neph Sy	36.36
Zinc Oxide	18.18
EPK	9.09
Flint	36.36
Chrome Oxide	1.00
Water	80



1-3 Second Dip



2-3 Second Dips




Reduction



Oxidation

UMF

SiO ₂ :Al ₂ O ₃ Ratio 9.29 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.41	Collective "Al ₂ O ₃ " 0.37	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.37	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

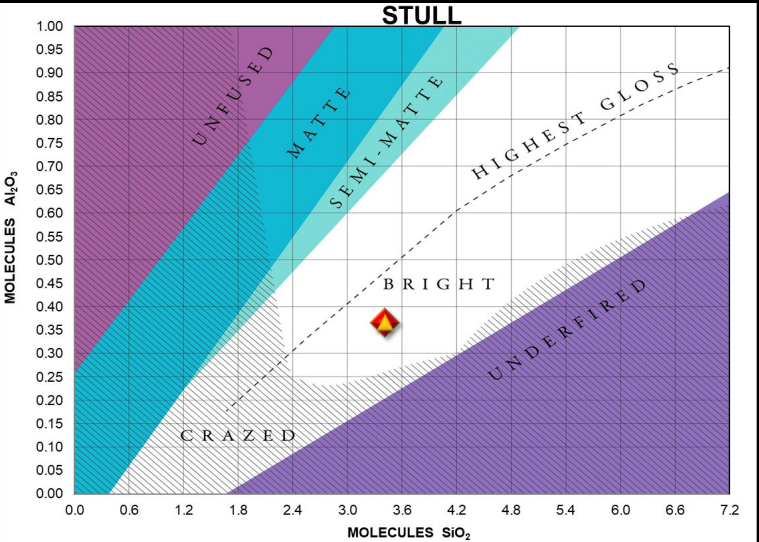

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 9.29 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.41	Collective "Al ₂ O ₃ " 0.37	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.37	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop

Zinc Pinc

Mapping
Silica 6

030823-34

Neph Sy	33.00
Zinc Oxide	16.50
EPK	8.25
Flint	41.25
Chrome Oxide	0.99
Water	60



1-3 Second Dip



2-3 Second Dips




Reduction



Oxidation

UMF

SiO ₂ :Al ₂ O ₃ Ratio 10.57 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.90	Collective "Al ₂ O ₃ " 0.37	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.37	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃	ZrO ₂	P ₂ O ₅		MnO ₂	CoO

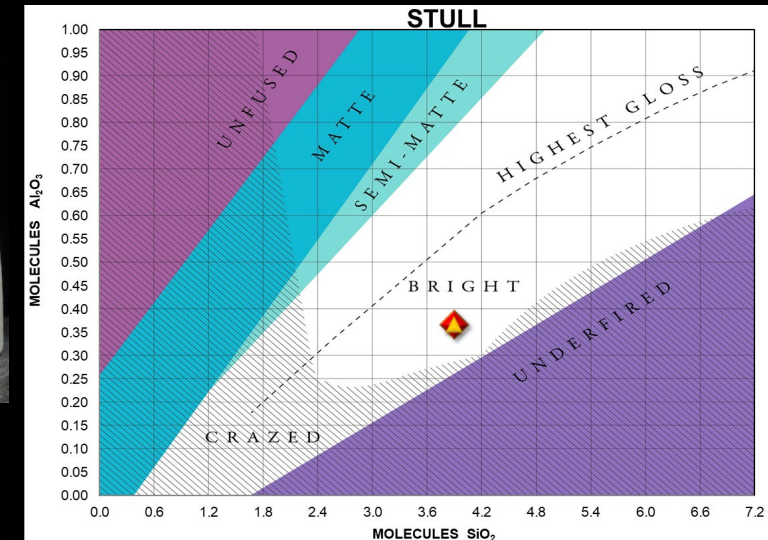

EUMF

SiO ₂ :Al ₂ O ₃ Ratio 10.57 : 1		Alkali Metals 0.25		Alkaline Earths 0.75	
SiO ₂ 3.90	Collective "Al ₂ O ₃ " 0.37	Na ₂ O 0.20	K ₂ O 0.06	MgO 0.00	CaO 0.01
B ₂ O ₃	Al ₂ O ₃ 0.37	Li ₂ O	CuO	SrO	BaO
TiO ₂ 0.00	NiO	Bi ₂ O ₃	SnO ₂	ZnO 0.73	FeO 0.01
Cr ₂ O ₃ 0.02	ZrO ₂	P ₂ O ₅		MnO ₂	CoO



Ceramic
Materials
Workshop